

Development of the Structure and Properties of Aluminium Alloy EN AW 6082 after Severe Plastic Deformation

Vývoj struktury a vlastností slitiny hliníku EN AW 6082 po extrémní plastické deformaci

Ing. Ladislav Kander¹; Ph.D., doc. Ing. Miroslav Greger, CSc.²; Ing. Jan Kander¹; doc. Ing. Petr Jonšta, Ph.D.¹

¹ MATERIÁLOVÝ A METALURGICKÝ VÝZKUM s.r.o., Pohraniční 693/31, Vítkovice, 703 00 Ostrava, Česká republika

² Vysoká škola báňská – Technická univerzita Ostrava, 17. listopadu 2172/15, 708 00 Ostrava-Poruba, Česká republika

Microstructure and texture development of an EN AW6082 alloy during equal channel angular pressing (ECAP) was investigated and correlated with the mechanical properties. The micro-structure was effectively refined by ECAP, and the original fibre texture of the extruded aluminium alloy was disintegrated, and a new texture was gradually developed by repetitive ECAP pressing. After 6 ECAP passes following the route B_c, the yield stress was lower than that of the as-extruded aluminium alloy, indicating that the texture softening was dominant over the strengthening due to grain refinement. Cross-section of original samples was 20 x 20 mm and their length was 125 mm. Deformation forces were measured during extrusion, resistance to deformation was calculated and deformation speed was determined approximately. Analysis of structure was made with use of light microscopy, TEM and SEM. Mechanical properties of the samples after extrusion were determined by tensile test and by the so-called penetration test.

Key words: micro-structures; properties; aluminium alloy; ECAP

Experimentálně byl ověřován vývoj mikrostruktury a mechanických vlastností slitiny hliníku EN AW 6082 při aplikaci extrémní plastické deformace protlačováním úhlovými kanály (ECAP) a stanoven vztah mezi strukturou a mechanickými vlastnostmi. Příčný průřez výchozích vzorků byl 20 x 20 mm, délka vzorků 125 mm. Vzorky byly protlačovány při teplotě místnosti. Pro zvýšení koncentrace a zrovnoměnění deformace v objemu vzorku byly vzorky po jednotlivých protlačeních pootočený kolem podélné osy o 90° a znovu protlačovány (cesta B_c). Při aplikaci extrémní plastické deformace technologií ECAP probíhá intenzivní zjemňování zrna, už v počátečních průchodech vzorků maticí, ale deformace je v objemu vzorků nerovnoměrná. Se zvyšujícím se počtem průchodů vzorků maticí je intenzita zjemňování zrna menší, avšak velikost jednotlivých zrn je rovnoměrnější. Jednotlivá zrna jsou přednostně orientována ve směru hlavní deformace. Po šesti průchodech ECAP tažnost slitiny EN AW 6082 klesá i když zjemnění zrna bude pokračovat i při zvýšeném počtu průchodů ECAP. Při aplikaci ECAP byly měřeny deformační síly, vypočítány deformační odpory v jednotlivých průchodech, stanovena optimální deformační rychlost a teplota deformace se pohybovala pod teplotou rekrystalizace zpracovávané slitiny EN AW 6082. Rozbor struktury byl proveden pomocí světelné mikroskopie, pomocí TEM a SEM. Mechanické vlastnosti vzorků po protlačování byly stanoveny zkouškou tahem a provedením penetračního testu. Využití extrémní plastické deformace pro zvýšení mechanických vlastností Al slitin je v současné době stále ve stádiu laboratorních zkoušek.

Klíčová slova: micro-structures; properties; aluminium alloy; ECAP

1. Introduction

Extrusion by ECAP method enables to obtain a fine-grained structure in larger volumes. Products made by this technique are characterized by high strength properties, Fig. 1.

$$\sigma_y = \sigma_0 + k d_g^{-\frac{1}{2}} \quad (1)$$

where σ_y is the yield stress, σ_0 is a material constant for the starting stress of dislocation movement (or the resistance of the lattice to dislocation motion), k is the strengthening coefficient (a constant unique to each material), and d_g is the average grain diameter.

The Hall–Petch relation (1) predicts that as the grain size decreases, the yield strength increases. The Hall–Petch relation was experimentally found to be an effective model for materials with grain sizes ranging from 1 millimeter to 1 micrometer [2-4]. Consequently, it was believed that if the average grain size was decreased even more to the nanometer length scale, the yield strength would increase as well [5-7]. However, experiments on many nano-crystalline materials demonstrated that if the grains reached the critical grain size, which was typically less than 100 nm, the yield strength would either remain constant or decrease with the decreasing grain size [8]. This phenomenon has been termed as reverse or inverse Hall–Petch relation. A number of different mechanisms

have been proposed for this relation. As suggested by Poková et al. [9], they fall into four categories: (1) Dislocation based, (2) Diffusion based, (3) Grain boundary shearing based, (4) Two phase based [10, 11]. Other explanations, that have been proposed to rationalize the apparent softening of metals with nano-sized grains, include poor sample quality and suppression of dislocation pileups. Many of the early measurements of reverse Hall–Petch effect were likely the result of unrecognized pores in samples. The presence of voids in nano-crystalline metals would undoubtedly lead to their weaker mechanical properties. The pileup of dislocations at grain boundaries is a signature mechanism of the Hall–Petch relationship [12, 13]. However, once grain sizes drop below the equilibrium distance between dislocations, this relationship should no longer be valid. Nevertheless, it is not entirely clear what exactly the dependency of yield stress should be on grain sizes below this point.

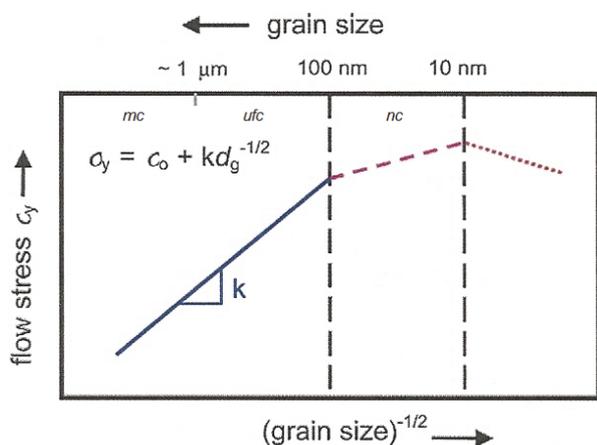


Fig. 1 Schematic representation of the variation of yield stress as function of grain size in mc, ufc and nc metals and alloys

Obr. 1 Závislost meze kluzu na velikosti zrna pro hrubozrnné (mc), ultrajemnozrnné (ufc) a nanostrukturní (nc) materiály

2. Development and structure

Influence of amount of plastic deformation on properties of metallic materials is connected with an increase of internal energy. Internal energy increases right to the limit value, which depends on the manner of deformation, purity, grain size, temperature, etc. As a result of inhomogeneity of deformation caused by the ECAP technique the internal energy gain differs at different places of the formed alloy. For example, the value of internal energy is different in slip planes, at boundaries and inside cells. It is possible to observe higher internal energy also in proximity of precipitates, segregations and solid structural phases. For usual techniques, pure metals, medium amount of deformation and temperatures, the values of stored energy are said to be approx. around $10 \text{ J} \cdot \text{mol}^{-1}$ [14]. In cold extrusion density of dislocations increases with magnitude of plastic deformation. Density of dislocations depends linearly on amount of plastic deformation in accordance with the well-known Eq. (2) [15, 16]:

$$\rho = \rho_0 + K \cdot \varepsilon \quad (2)$$

where ρ_0 is initial dislocation density (10^{10} to 10^{12} m^{-2}), K is a constant, ε is amount of deformation.

Flow stress necessary for continuation of deformation is function of number of lattice defects as stated by Eq. 3 [17, 18]:

$$\tau = \tau_0 + k \cdot G \cdot b \cdot \rho^{\frac{1}{2}} \quad (3)$$

Where τ_0 is initial flow stress, k is a constant ($k = 0.3$), G , is modulus of elasticity in shear ($G \sim 25 \text{ GPa}$) and b is Burgers vector ($b = 0.3$ to 0.4 nm)

3. Experimental procedures

The objective of experiments was to verify deformation behaviour of the given alloy, determine its resistance to deformation, formability and change of structure in extrusion of this alloys. Experiments were made with use of an apparatus, the diagram of which is shown in Fig. 2. Chemical composition the alloy is given in Tab. 1.

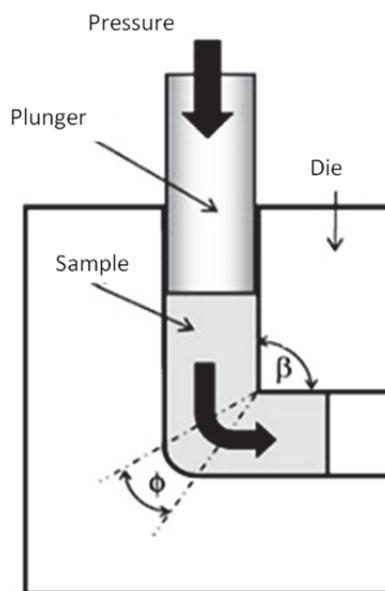


Fig. 2 Schematic illustration of a die used at the present investigation: a) with $\Phi = 90^\circ$ and $\psi = 20^\circ$

Obr. 2 Schématické znázornění tvaru zápustky ECAP: a) s vnitřním úhlem kanálů $\Phi = 90^\circ$ a vnějším úhlem kanálů $\psi = 20^\circ$

Tab. 1 Chemical composition of the EN AW 6082 alloy

Tab. 1 Chemické složení slitiny hliníku EN AW 6082

Contents of elements	Mg	Si	Mn	Fe	Cu	Zn	Ti	Cr	Al
[wt. %]	1.10	0.88	0.92	0.45	0.09	0.20	0.09	0.70	balance

During the process a metal billet is pressed through a die consisting of two channels, equal in cross section and intersecting at an angle Φ . The billet undergoes essentially simple shear deformation, but it retains the same cross-sectional geometry, so that it is possible to repeat the pressings for a number of passes, each one refining the grain to the extent, which is determined by the material characteristics.

Deformation forces were measured during extrusion and pressures in the die were calculated. At extrusion with the radius of rounding of edges ($R_y = 2$ mm; $R_{yn} = 5$ mm) the pressure in the die varied at the 1st pass around $\sigma_{max} = 620$ MPa, and it gradually increased in such a manner that at the fourth pass its value was approximately $\sigma_{max} = 810$ MPa. At extrusion through a die with smaller radii of rounding ($R_y = 0.5$ mm; $R = 2$ mm) the pressure at the first pass was approx. $\tau_{max} = 780$ MPa, and at the third pass it was approx. $\tau_{max} = 1560$ MPa. Significantly higher values of resistance to deformation and strengthening at extrusion are related to high absolute value of octahedral stress, which either contributes to more difficult formation of dislocations or decelerates their movement.

Another factor, which influences flow stress and development of micro-structure significantly, is the angle Φ , which is formed by the axis of vertical and horizontal channel. This angle determines magnitude of in individual passes, and it can be expressed by Eq. (4) [19, 21]:

$$\gamma = 2 \cotg(\Phi/2) \quad (4)$$

Shear strain at the angle $\Phi = 90$ reaches the value of 2, and normal deformation reaches 2.3. Smaller angle Φ leads to higher shear stress at each pass. We have checked the size of the angle Φ in the range from 90° to 120° with use of technological route B_C. We have ascertained, that refining of grains is the most efficient (under the same magnitude of deformation), at the angle of 90° . This is given by the fact that two slip planes in the sample make in this case the angle of 60° . For materials, forming of which is more difficult, it is more advantageous to apply the angle $\Phi = 120^\circ$ together with higher extrusion temperature. It is possible to calculate the magnitude of accumulated deformation from the Eq. (5) [1, 22]:

$$\epsilon_N = \frac{N}{\sqrt{3}} \left[2 \cotg g \left(\frac{\phi}{2} + \frac{\psi}{2} \right) + \psi \cos ec \left(\frac{\phi}{2} + \frac{\psi}{2} \right) \right] \quad (5)$$

where N is number of passes through a die, Φ is angle channels, Ψ is additional angle.

Values of total accumulated deformation, grain size and mechanical properties of the sample after increasing number of passes are shown in Tab. 2.

Tab. 2 Effective strain intensity, grain size, and mechanical properties samples EN AW 6082 after ECAP

Tab. 2 Nárůst intenzity deformace, velikost zrna a mechanické vlastnosti vzorků slitiny EN AW 6082 po jednotlivých průchodech ECAP

Number of passes	Total strain intensity	Equivalent area reduction	Grain size	0.2% YS	UTS	$\frac{UTS}{0.2\%YS}$	Elong.	$\bar{\sigma}$ $\bar{\sigma} = C \cdot \epsilon^n$
	[ε]	[%]	[μm]	[MPa]			[%]	[MPa]
0	-	-	50	120	185	1.50	15.5	175.10
1	1.15	69	3.5	190	230	1.20	8.5	179.95
2	2.30	90	2.0	217	252	1.15	7.5	206.90
3	3.45	97	1.5	230	283	1.20	6.5	224.30
4	4.60	99	1.1	250	312	1.25	6.0	237.65
5	5.75	99.8	1.0	265	325	1.25	5.5	248.30
6	6.90	99.9	0.9	275	340	1.25	5.5	257.50

4. Experimental result and discussion

4.1 Micro-structure

Structure of initial original samples is shown in Fig. 3 and structure of samples after individual passes is shown in Fig. 4.

The structure contains ordinary inter-metallic phases corresponding to the given composition of the alloy. Average grain size in transverse direction was determined by quantitative metallography methods and it varied around 50 μm. Change of shape of the front and rear end of the sample and maintenance of integrity at individual stages of extrusion depend on the level of lubrication and on radii of edges (R_v , R_{vn}) of the extruding channel. After individual passes accumulation of deformation strengthening occurred, the basis of which was in the formed sub-structure, which can be seen in Fig. 5.

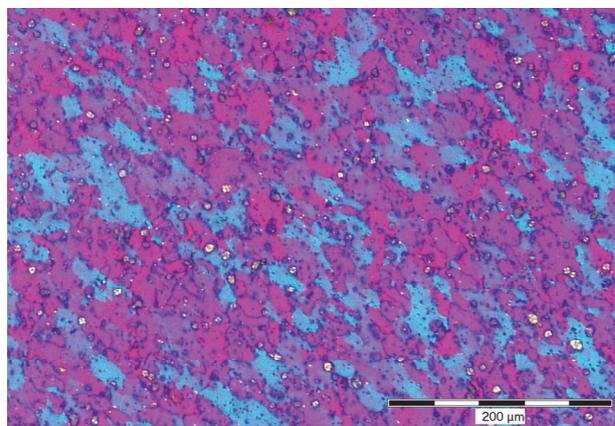


Fig. 3 Microstructure of initial sample EN AW 6082 alloy
Obr. 3 Počáteční mikrostruktura slitiny EN AW 6082

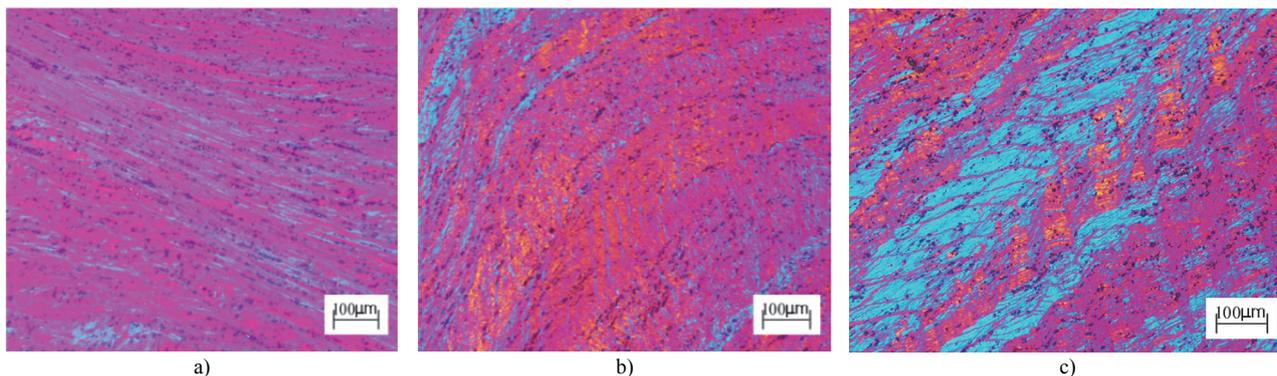


Fig. 4 Microstructure of the samples EN AW 6082 after ECAP extrusion in longitudinal direction: a) after the 1st pass b) after the 2nd pass c) after the 3rd pass

Obr. 4 Mikrostruktura vzorků slitiny hliníku 6082 po protlačování ECAP: a) po 1. průchodu, b) po 2. průchodu, c) po 3. průchodu

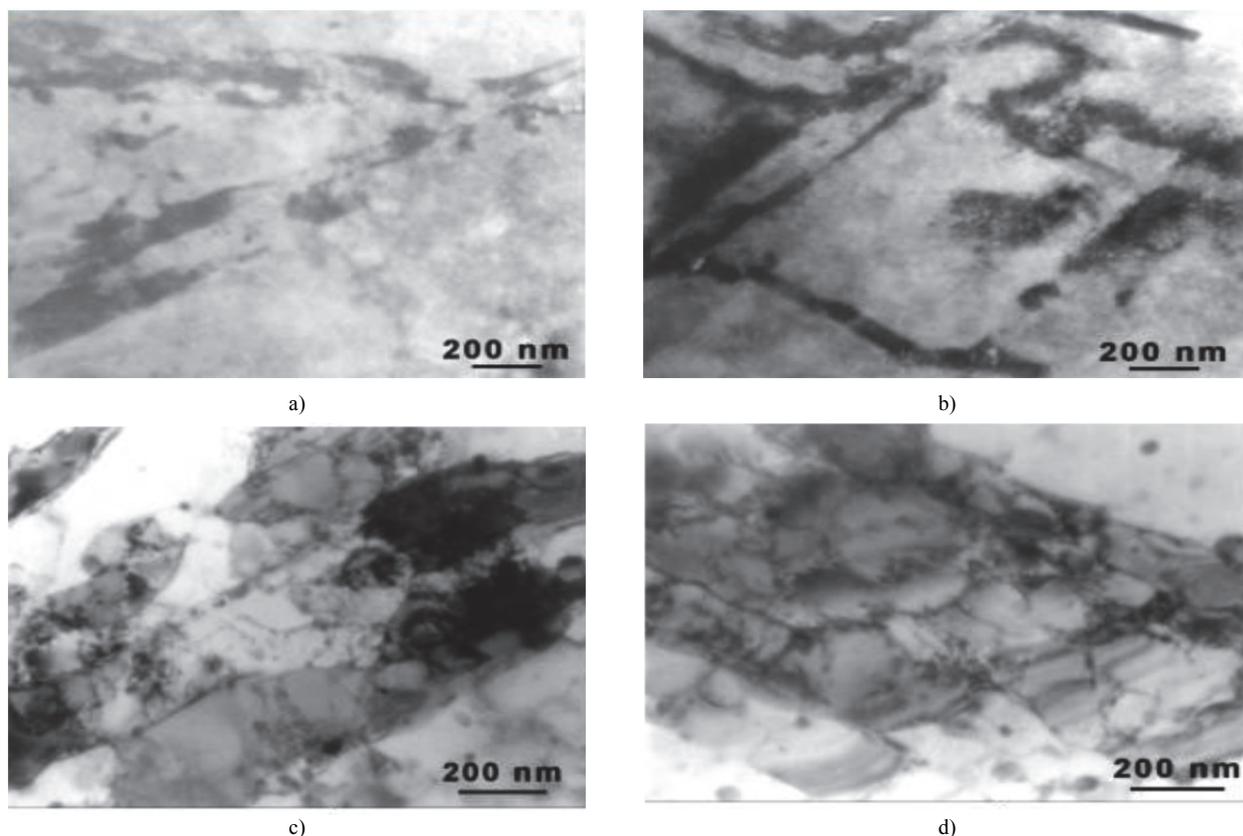


Fig. 5 Sub-structure of 6082 alloy after ECAP extrusion: a) after the 1st pass, b) after the 2nd pass, c) after the 3rd pass, d) after the 4th pass

Obr. 5 Substruktura slitiny hliníku 6082 po jednotlivých průchodech ECAPem: a) po 1. průchodu, b) po 2. průchodu, c) po 3. průchodu, d) po 4. průchodu.

4.2 Mechanical properties determined by tensile test

We have verified influence of rectangular extrusion on mechanical properties with use of classical mechanical tensile test and the so-called small punch test. Miniature test specimens were made from samples after application of the ECAP technique for the tensile test.

Obtained values of tensile strength vary for the aluminium alloy within the range from UTS = 185 to 340 MPa. Obtained values of tensile strength correspond very well with the values obtained by simulation and with approximate values based on the results of measurements of hardness. In the frame of evaluation of influence of the ECAP technique on mechanical properties, samples

without application of the ECAP technique were submitted to tensile test also. We have tested altogether 4 test specimens with cross-section of 2.5 × 5 mm.

From realized experiment we have determined tensile strength for the 6052 alloy, without ECAP, to be UTS = 185 MPa.

As it follows from comparison of strength properties resulting from rectangular extrusion, the strength of the aluminium alloy was increased approximately by 86.5 %. We have performed a fractography analyses on broken halves of test specimens. Results of the above mentioned analyses, including their graphical presentations are given below.

4.3 Mechanical properties determined by small punch test

Three test specimens in the form of disc with diameter of 8 mm and thickness of 0.5 mm [23] were made from the samples after application of the ECAP technique.

Basic mechanical properties were determined from small punch test, the principle of which consists in penetration of special puncher with spherical surface through the flat disc-shaped sample, which is fixed between the upper holder and the lower die. From said experiments, it is possible to state that tensile strength of the aluminium alloy EN AW 6082 obtained by small punch test varies in the range from UTS = 325 to 345 MPa, which demonstrates very good agreement with the values of tensile strength obtained by the standard tensile test (UTS = 335 to 340 MPa).

5. Conclusion

We have experimentally verified behaviour of the EN AW 6082 aluminium alloy after extrusion. ECAP method is a potential tool for refining of grain in polycrystalline metals. This procedure makes it possible to obtain the grain size of approx. 1 μm after 6 passes. In order to obtain an optimum microstructure, it is necessary to apply more passes with turning of the sample between individual passes by 90° around the longitudinal axis. After 4 passes development of sub-structure occurs. When the die with the angle of 90° is used more intensive deformation is achieved and resistance to deformation is higher than at extrusion with higher angles. Radii of working edges of extruding channel must correspond to conditions for laminar flow of metal.

Acknowledgement

„This paper was created as part of the drawing and use of institutional support for Long-term and conceptual development of a research organization in 2022, provided by the Ministry of Industry and Trade of the Czech Republic“.

References

- [1] VALIEV, R.Z. and LANGDON, T. G. Principles of equal-channel angular pressing as a processing tool for grain refinement. *Progr. Mater. Sci.* 51 (2006) 881–981.
- [2] HORITA, Z., FUJINAMI, T., NEMOTO, M. and LANGDON, T.G. Equal-channel angular pressing of commercial aluminium alloys: Grain refinement, thermal stability and tensile properties. *Met. Mater. Trans. A*. 31 (2000), 691–701.
- [3] XU, C., SZÁRAZ, Z., TROJANOVÁ, Z., LUKÁČ, P. and LANGDON, T.G. Evaluating plastic anisotropy in two aluminium alloys processed by equal-channel angular pressing. *Mater. Sci. Eng. A*. 497 (2008), 206–211.
- [4] VALIEV, R. Z., ZHILYAEV, A.P. and LANGDON, T.G. Bulk Nanostructured Materials: Fundamentals and Applications; John Wiley & Sons, Inc.: Hoboken, NJ, USA, 2014.
- [5] LIU, M., ROVEN, H.J., YU, Y. and WERENSKIOLD, J.C. Deformation structures in 6082 aluminium alloy after severe plastic deformation by equal-channel angular pressing. *Mat. Sci. Eng. A*. 483 (2008), 59–63.
- [6] LACKOVÁ, P., MILKOVIČ, O., BURŠÁK, M. and KVACKAJ, T. The Influence of Severe Plastic Deformation on Structure and Mechanical Properties the Aluminium Alloy EN AW 6082. *Key Eng. Mat.* 635 (2014), 18–21.
- [7] RAVISANKAR BALASUBRAMANIAN. Equal-Channel Angular pressing (ECAP). In *Aliofkhaezei Mahmood*, editor. Chapter 13 in handbook of mechanical nanostructuring; 2015.
- [8] JIANG, D., NING, J., SUN, J., HU, Z. and HOU, Y. Annealing Behavior of Al-Mg-Mn Alloy Processed by ECAP at Elevated Temperature. *Transaction of Nonferrous Metals Society of China*, 18 (2018), 248–254.
- [9] POKOVÁ, M., ZIMINA, M. and CIESLAR, M. The Influence of ECAP on Microstructure Evolution of Aluminium Alloys During in-situ Heating in TEM. *International Journal of Materials Research*, 106 (2015) 7, 676–681.
- [10] GUPTA, A., CHANDRASEKHAR, B. and SAXENA, K.K. Effect of Equal Channel Angular Pressing on Mechanical Properties: An overview. *Mater. Today Proc.* 45 (2021), 5602–5607.
- [11] ABIOYE, O.P., ATANDA, P.O., OSINKOLU, G.A., ABIOYE, A.A., OLUMOR, I.D., ODUNLAMI, O.A. and AFOLALU, S.A. Influence of Equal Channel Angular Extrusion on the Tensile Behavior of Aluminium 6063 Alloy. *Procedia Manuf.* 35 (2019), 1337–1343.
- [12] HOWEYZE, M., ARABI, H., EIVANI, A. and JAFARIAN, H. Strengthening of AA5052 Aluminium Alloy by Equal Channel Angular Pressing Followed by Softening at Room Temperature. *Mater. Sci. Eng. A*. 72 (2018), 160–168.
- [13] CABIBBO, M. Microstructure Strengthening Mechanism in Different Equal Channel Angular Pressed Aluminium Alloys. *Materials Science and Engineering A*, 560 (2013), 413–432.
- [14] SNOPIŃSKI, P., TAŃSKI, T. and KRÓL, M. Effect of SPD Processing on the Structure and Properties of Al-Mg Alloy. *Inżynieria materiałowa*. (2018), 4–9.
- [15] DERAKHSHAN, J.F., PARSAN, M. and JAFARIAN, H. Microstructure and mechanical properties variations of pure aluminium subjected to one pass of ECAP-Conform process. *Mater. Sci. Eng. A*. 747 (2019), 120–129.
- [16] CERRI, E., DE MARCO, V. and LEO, P. FEM and metallurgical analysis of modified 6082 aluminium alloys processed by multipass ECAP: Influence of material properties and different process settings on induced plastic strain. *J. Mater. Proc. Techn.* 209 (2009) 3, 1550–1564.
- [17] MURASHKIN, M., SABIROV, I., KAZYKHANOV, V., BOBRUK, E., DUBRAVINA, A. and VALIEV, R. Z. Enhanced Mechanical Properties and Electrical Conductivity in Ultra-Fine Grained Al Alloy Processed via ECAP-PC. *J. Mater. Sci.* 48 (2013), 4501–4509.
- [18] MACKENZIE, P.W.J. and LAPOVOK, R. ECAP with Back Pressure for Optimum Strength and Ductility in Aluminium Alloy 6016. Part 1: Microstructure. *Acta Mater.* 58 (2010), 3198–3211.
- [19] ANGELLA, G., BASSANI, P., TUISSI, A. and VEDANI, M. Aging Behaviour and Mechanical Properties of a Solution Treated and ECAP Processed 6082 Alloy. *Materials Transactions*, 45 (2004) 7, 2282–2287.
- [20] GUPTA, A., SAXENA, K., BHARTI, A., LADE, J., CHADHA, K. and PARESI, P.R. Influence of ECAP Processing Temperature and Number of Passes on Hardness and Microstructure of Al-6063. *Adv. Mater. Process. Technol.* (2021), 1–12.
- [21] JIANG, J.F., YING, W., LIU, Y.Z., XIAO, G.F. and HUA, L. Microstructure and Mechanical Properties of 7005 Aluminium Alloy Processed by one-pass Equal Channel Reciprocating Extrusion. *Trans. Nonferrous Met. Soc. China*, 31 (2021), 609–625.
- [22] BARENJI, A.B., EIVANI, A., HASHEMINIASARI, M., JAFARIAN, H. and PARK, N. Effects of Hot Forming Cold die Quenching and Inter-Pass Solution Treatment on the Evolution of Microstructure and Mechanical Properties of AA2024 Aluminium Alloy after Equal Channel Angular Pressing. *J. Mater. Res. Technol.* 9 (2020), 1683–1697.
- [23] GREGER, M. and KANDER, L. Evaluation of Mechanical Properties of Ultra-Fine Grain Titanium Using Small Punch Tests. In 5th Int. Conf. *NANOCON 2013*. Brno (Czech Republic): Tanger, s.r.o., 2013, 560–565. ISBN 978-80-87294-44-4.